

High-pressure synthesis of quantum magnet M -YbTaO₄ with a stretched diamond lattice

Nicola D. Kelly^{1,2,*}, Xuan Liang², Siân E. Dutton^{1,†}, Kazunari Yamaura², and Yoshihiro Tsujimoto^{2,‡}

¹*Cavendish Laboratory, University of Cambridge, J J Thomson Avenue, Cambridge CB3 0US, United Kingdom*

²*Research Center for Materials Nanoarchitectonics (MANA), National Institute for Materials Science (NIMS), 1-1 Namiki, Tsukuba, Ibaraki 305-0044, Japan*



(Received 13 November 2025; accepted 6 February 2026; published 25 February 2026)

We report bulk magnetic properties of ytterbium tantalate in its monoclinic fergusonite modification, M -YbTaO₄. The spin- $\frac{1}{2}$ Yb³⁺ ions in this phase are arranged on a geometrically frustrated “stretched diamond” lattice. M -YbTaO₄ cannot be prepared at ambient pressure and was instead prepared in a belt-type apparatus at 6 GPa and 1800 °C. Susceptibility and specific heat data show no long-range ordering down to 1.8 K and are consistent with a $J_{\text{eff}} = \frac{1}{2}$ Kramers doublet which splits in an applied field. Furthermore, under high-pressure synthesis the entire solid solution YbNb_{*x*}Ta_{1-*x*}O₄ ($0 \leq x \leq 1$) can be stabilized in the M phase, in contrast to ambient-pressure synthesis which favors the competing M' phase for Ta-rich compositions. Subsequent annealing of the Nb-Ta mixed samples resulted in color changes, suggesting oxygen deficiency in some of the as-prepared high pressure samples. There was little variation in the bulk magnetic properties upon varying either the Nb/Ta ratio or the annealing conditions.

DOI: [10.1103/3xqz-qzr7](https://doi.org/10.1103/3xqz-qzr7)

I. INTRODUCTION

Synthesis under high pressure is an important tool to stabilize novel phases of condensed matter. It has been used to synthesize compounds from many different chemical and structural families, including borates [1–3], oxychalcogenides [4,5] and oxyhalides [6], nitrides [7], simple, double, triple, and quadruple perovskite oxides [8–12], and many others, often with unusual magnetic or electronic properties such as incommensurate magnetic order. High-pressure-high-temperature synthesis is a particularly powerful technique to stabilize cations in unusual oxidation states or coordination environments [11], allowing the synthesis of metastable phases that would not be accessible at ambient pressure.

Solid-state materials with the magnetic ions located on a diamond-like lattice have gained significant attention in recent years. In a perfect cubic diamond system, such as the A sites of spinels like MnAl₂O₄ [13] or CoRh₂O₄ [14], all the nearest-neighbor interactions between magnetic ions are identical, forming a network where every magnetic ion is surrounded by four others in a tetrahedral arrangement. Considering only the nearest-neighbor exchange interactions (J_1), spins on a cubic diamond lattice are expected to display long-range three-dimensional order. Both MnAl₂O₄ and CoRh₂O₄

are antiferromagnets with Néel temperatures of 40 and 25 K, respectively. However, nonzero next-nearest-neighbor interactions J_2 can also compete with J_1 , sometimes significantly suppressing long-range order [15] or at other times promoting a glassy state [13,16], showing that the cubic diamond lattice is already a rich landscape for different magnetic behaviors. In contrast, in tetragonal or hexagonal crystal structures such as those of LiYbO₂ [17] or β -KTi(C₂O₄)₂ · 2H₂O [18], the distances remain identical but the angles between adjacent spin-spin interactions are distorted away from the ideal 109.5°, leading to competition between different interactions. Especially when there are nonzero J_2 interactions, such a network can also host strong geometric magnetic frustration [14,19–21]. Further distortion or “stretching” of the diamond lattice occurs in monoclinic systems, such as the lanthanide metaborates $Ln(\text{BO}_2)_3$ [22], niobates $Ln\text{NbO}_4$, and tantalates M - $Ln\text{TaO}_4$ [23]. This is shown schematically in Fig. 1(a). In monoclinic crystal structures, each point on the stretched diamond lattice has two distinct pairs of near neighbors, shown as red (shorter) and blue (longer) lines, compared with the cubic diamond lattice where each point has four neighbors at the same distance, shown as black lines. Since the exchange between the magnetic ions depends on overlapping atomic orbitals, the strength of magnetic exchange will be different for the different interatomic distances, possibly leading to magnetic frustration. Frustration effects in compounds with a stretched diamond lattice have been linked to observations of unusual magnetic behavior including incommensurate helical order [21]. Furthermore, strong spin-orbit coupling and crystal electric field effects also play an important part in the magnetism of lanthanide-based compounds.

A recent study focused on the series of compounds M - $Ln\text{TaO}_4$ ($Ln = \text{Nd–Er}$) with a monoclinic stretched diamond lattice of magnetic Ln^{3+} ions. None of the compounds

*Contact author: ne281@cam.ac.uk

†Contact author: sed33@cam.ac.uk

‡Contact author: tsujimoto.yoshihiro@nims.go.jp

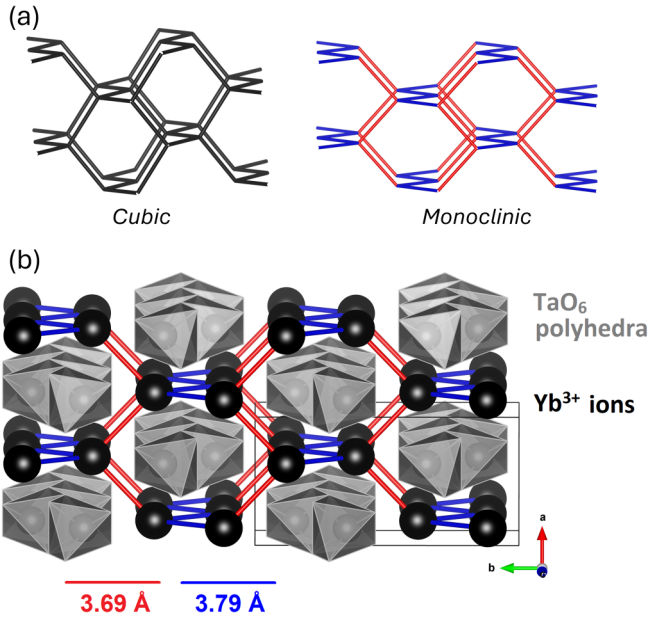


FIG. 1. (a) Schematic illustrating the cubic diamond lattice (all nearest-neighbor distances are equal, shown as black lines) and the “stretched diamond lattice” in monoclinic systems (inequivalent distances between neighboring points, shown as red and blue lines). (b) Crystal structure of $M\text{-YbTaO}_4$, space group $I2/a$ (no. 15). Yb^{3+} ions are shown in black and Ta^{5+} ions in gray; oxide ions are located at the vertices of the TaO_6 polyhedra. The red and blue solid lines indicate the two closest Yb–Yb distances making up the stretched diamond lattice.

orders above 1.8 K except $M\text{-TbTaO}_4$, which displays A -type antiferromagnetic (AFM) order below $T_N = 2.25$ K [23]. In an applied field the compound undergoes a spin-flop-type transition to ferromagnetic (FM) at 6 T and 1.6 K and there is evidence for magnetoelectric coupling [24]. Furthermore, Kumar *et al.* have recently studied the isostructural ytterbium niobate YbNbO_4 using magnetic susceptibility, heat capacity, and muon-spin relaxation (μSR) spectroscopy. Their observations exclude the possibility of either long-range order or spin freezing and indicate that the Yb^{3+} spins remain correlated and strongly fluctuating down to 300 mK, making YbNbO_4 a potential spin liquid candidate [25].

The M phase of YbTaO_4 is isostructural with YbNbO_4 and therefore also hosts a stretched diamond lattice; see Fig. 1(b). The presence of two competing Yb–Yb interactions with similar interatomic distances is expected to produce geometric magnetic frustration. It is not possible to prepare $M\text{-YbTaO}_4$ at ambient pressure and all previous reports [26,27] have utilized high-pressure synthesis. To our knowledge no magnetic studies have been carried out on this phase. In this work, we synthesized $M\text{-YbTaO}_4$ with high reproducibility using a belt-type high-pressure apparatus at 1800 °C and 6 GPa and measured its bulk magnetic properties down to 1.8 K. $M\text{-YbTaO}_4$ shows no long-range order in this temperature range and magnetometry and specific heat data support an effective $J = \frac{1}{2}$ Kramers doublet state. We also synthesized the solid solution $\text{YbNb}_x\text{Ta}_{1-x}\text{O}_4$ ($0 \leq x \leq 1$) under both ambient- and high-pressure conditions. Under ambient pressure, Nb-rich samples crystallize in the M phase with a

stretched diamond lattice while Ta-rich samples favor the competing M' phase with a distorted 2D square lattice of Yb^{3+} ions [28,29]. In contrast, high-pressure synthesis allows the pure M phase to be stabilized for all x . However, the reducing environment of the high-pressure synthesis resulted in colored samples for some values of x , which was ascribed to oxygen deficiency; the color changed to white after annealing under ambient pressure in either air or O_2 .

II. EXPERIMENTAL METHODS

A. Synthesis

Appropriate stoichiometric amounts of Yb_2O_3 (99.9%, Kojundo Chemical Laboratory Co. Ltd.), Nb_2O_5 (99.9%, Rare Metallic Co. Ltd.), and Ta_2O_5 (99.9%, Rare Metallic Co. Ltd.) for a target mass of 0.5 g $\text{YbNb}_x\text{Ta}_{1-x}\text{O}_4$ ($0 \leq x \leq 1$) were weighed accurately and ground together by hand. For ambient-pressure synthesis, the mixture was pressed into an 8 mm pellet, placed in an alumina crucible, and heated at 3°C min^{-1} to 1500 °C for 24 h in air. After cooling at the natural rate of the furnace, the resultant pellets were ground into fine white powders. For high-pressure synthesis, the mixture was sealed into a Pt capsule (inner diameter 6.9 mm, length ≈ 2.2 mm, and wall thickness ≈ 0.2 mm) and loaded into a belt-type press (Kobe Steel, Ltd.) [30] using a NaCl–pyrophyllite cell assembly with a graphite tube heater [31]. After cold pressurizing to 6 GPa, the samples were heated to 1800 °C at $100^\circ\text{C min}^{-1}$, held for 60 min, and quenched to below 100 °C within 30 s while holding pressure. Pressure was then released over approximately 40 minutes and the product was recovered from the Pt capsules in the form of a white ($x = 0$) or beige ($x > 0$) fine powder. A sample of $M\text{-LuTaO}_4$ was synthesized from Lu_2O_3 (99.9%, Kojundo Chemical Laboratory Co. Ltd.) and Ta_2O_5 at 6 GPa, 1600 °C, 2 h; the product was a white powder.

B. Powder x-ray diffraction (PXRD)

Powder x-ray diffraction (PXRD) was carried out on a Rigaku MiniFlex600 diffractometer with $\text{Cu } K\alpha$ radiation, $\lambda = 1.541$ Å, range $5\text{--}70^\circ$, and step size 0.01° . Rietveld refinement [32] was carried out using TOPAS [33]. The zero offset and 12 background coefficients (Chebyshev polynomial) were refined, as were the unit cell dimensions and the y fractional coordinates of the lanthanide and transition metal sites. The fractional occupancies of the transition metal site by Nb and Ta were fixed at their nominal values according to the reaction stoichiometry. The peak shape was described by a modified Thompson-Cox-Hastings pseudo-Voigt function. A preferred orientation correction of order up to 8 was modeled using the spherical harmonics function in TOPAS.

C. Magnetometry

Magnetic measurements were made using a Quantum Design Materials Properties Measurement System (MPMS-3). 10–20 mg of sample (accurately measured each time) was contained in clingfilm inside a plastic straw as the sample holder. The dc magnetic moment was measured as a function of temperature upon warming in the range 1.8–300 K at a field

of 500 Oe, after cooling in zero field (ZFC) or in the applied field (FC). The dc moment was also measured as a function of magnetic field in the range 0–7 T at several temperatures. The data were corrected for the presence of up to 5 wt.% nonmagnetic PtO (exact value determined by Rietveld refinement for each sample).

D. Specific heat

Approximately 50 mg of $M\text{-YbTaO}_4$ was pressed into a pellet of diameter 5 mm and thickness about 1 mm. In order to increase the pellet's hardness, it was annealed in air for 2 h at 800 °C, which is low enough to prevent transformation to the M' phase [27] as confirmed by postannealing PXRD. A portion of the pellet weighing 8.50 mg was attached to the sample holder using Apiezon N grease and the heat capacity was measured at $T = 2\text{--}60$ K using a Quantum Design Physical Properties Measurement System (PPMS) EverCool II.

The lattice contribution C_{latt} was modeled using the Debye law:

$$C_{\text{latt}} = \frac{9nRT^3}{\theta_D^3} \int_0^{\frac{\theta_D}{T}} \frac{x^4 e^x}{(e^x - 1)^2} dx, \quad (1)$$

where n is the number of atoms per formula unit, R is the molar gas constant, T is the temperature in K, and θ_D is the Debye temperature in K [34]. A scalar parameter p was included in the fitting equation and refined to account for the sample mass error and imperfect coupling to the sample stage, since the title compound is an insulator. The lattice contribution was then subtracted from the total heat capacity to leave the magnetic contribution, $C_{\text{mag}}(T)$.

III. RESULTS

A. Synthesis and structural characterization

Reaction of equimolar amounts of Ln_2O_3 and Ta_2O_5 in air under ambient-pressure conditions produces $M\text{-LnTaO}_4$ for $\text{Ln} = \text{Nd--Er}$ [23]. However, the required synthesis temperature increases across the Ln series and application of pressure is necessary to favor $M\text{-YbTaO}_4$ over the layered M' polymorph. Brixner and Chen [26] successfully synthesized $M\text{-YbTaO}_4$ at 1400 °C and 6 GPa, while Markiv *et al.* [27] used 1500 °C and 8 GPa. Our experiments found that 1 h at 6 GPa and 1800 °C, or alternatively 2 h at 6 GPa and 1700 °C, reliably produced $M\text{-YbTaO}_4$ without any reflections from the competing M' phase. The discrepancies between the different synthesis temperatures for our study compared with the literature results is most likely related to the calibration methods of the high-pressure apparatus, where the set point is typically specified by an electrical power rather than an absolute temperature value. All high-pressure reactions at elevated temperatures produced small amounts of PtO from oxidation of the Pt capsule, visible as shiny gray residue on the surfaces of the sample. This proved difficult to separate from the target phase and was therefore present at up to 5 wt.% in the final products. A prereaction at ambient pressure (to form the M' phase) was also tested but was less successful than starting from the binary oxides. All synthesis attempts and results are summarized in the Supplemental Material [35].

TABLE I. Refined structural parameters for $M\text{-YbTaO}_4$ and $M\text{-LuTaO}_4$ synthesized at high pressure. Space group $I2/a$, Cu $K\alpha$ radiation, and room temperature.

	$M\text{-YbTaO}_4$ (NK080)	$M\text{-LuTaO}_4$ (NK060)
a (Å)	5.2692(2)	5.25080(12)
b (Å)	10.8388(4)	10.8126(3)
c (Å)	5.03159(18)	5.02333(11)
β (deg)	95.4562(13)	95.3906(14)
V (Å ³)	286.061(19)	283.937(11)
R_{wp} (%)	9.92	7.73
χ^2	2.96	3.95
Yb1 (4e) x, y, z	[0.25, 0.1181(2), 0]	[0.25, 0.1172(3), 0]
Ta1 (4e) x, y, z	[0.25, 0.6482(2), 0]	[0.25, 0.6467(2), 0]
O1 (8f) x, y, z	(0.015, 0.719, 0.216)	(0.015, 0.719, 0.216)
O2 (8f) x, y, z	(0.901, 0.456, 0.240)	(0.901, 0.456, 0.240)

The crystal structure of $M\text{-YbTaO}_4$ was refined against room-temperature powder x-ray diffraction (PXRD) data using the Rietveld method [32]. The atomic coordinates for oxide ions were fixed at values from the literature for SmTaO_4 [36] because of the low x-ray scattering power of O compared with Yb and Ta; the isotropic thermal parameters U_{iso} were fixed at 1 Å² for all atoms. Table I gives the refined structural data for a representative sample of $M\text{-YbTaO}_4$ (NK080) and Fig. 2 shows the refinement. We chose the $I2/a$ setting of space group 15 because it gives the conventional cell with the smallest β angle [37]. However, other authors have previously reported the structure of $M\text{-YbTaO}_4$ using the nonconventional $B2/b$ setting [27]. After transforming that cell to $I2/a$, their reported lattice parameters agree well with our results and with those of Brixner and Chen [26]. The unit cell volume of $M\text{-YbTaO}_4$ also fits into the linear trend observed for the whole $M\text{-LnTaO}_4$ series; see Fig. 3. We could also synthesize the nonmagnetic analog $M\text{-LuTaO}_4$ using high pressure (6 GPa, 1600 °C, 2 h). Its structural parameters are consistent with the previous report [26] and are included in Table I for comparison with the Yb compound.

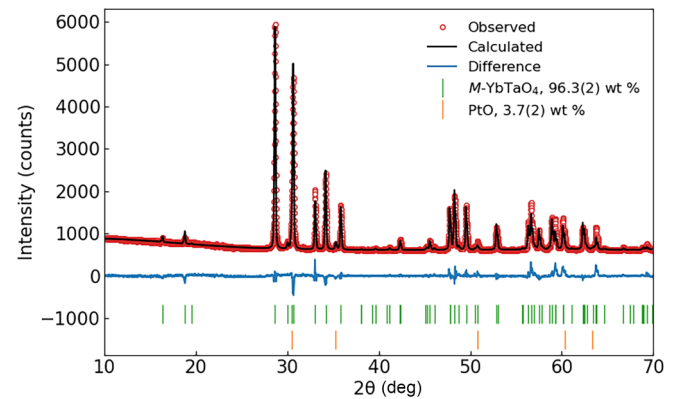


FIG. 2. Rietveld refinement against room-temperature PXRD data ($\lambda = \text{Cu } K\alpha$, 5–70°, 0.01° steps) for $M\text{-YbTaO}_4$. Red circles: observed data; black line: calculated pattern; blue line: difference pattern; green tick marks: Bragg reflection positions.

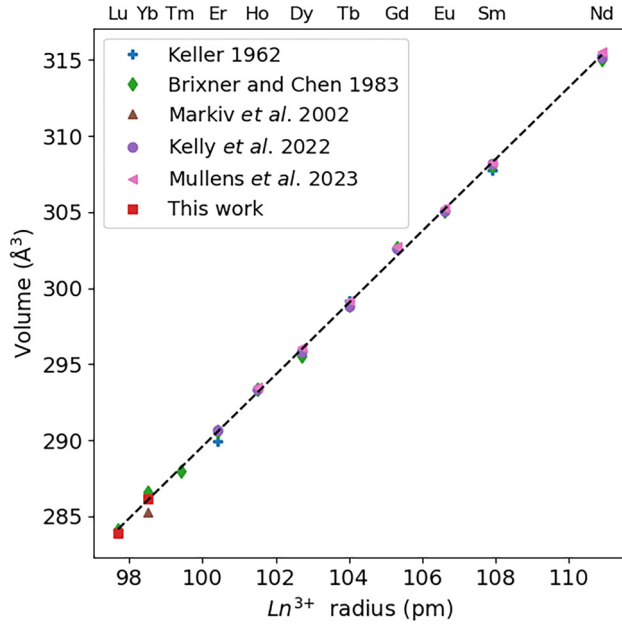


FIG. 3. Unit cell volume of M - Ln TaO₄ compounds [23,26,27,36,42] as a function of lanthanide ionic radius [43].

Note that somewhat high values of $\chi^2 > 2$ were obtained in the refinements of all high-pressure samples, indicating that the structural model does not completely capture the experimental diffraction data. We believe this is partially related to strong preferred orientation, which is a common feature of samples made under high-pressure conditions [38–40]. The extent of the preferred orientation effect, visible by eye as discrepancies between different Bragg reflection intensities, clearly varied between synthesis runs (see the Supplemental Material [35]). A correction for preferred orientation was included in all refinements but could not completely account for the variation in peak intensities. Furthermore, a synchrotron measurement in cylindrical capillary geometry (Supplemental Material) [35] also suffered from large χ^2 values, despite having much less preferred orientation. Other factors such as microstructural effects (strain) or local variation in the structure or composition may also be at play. We intend to investigate this in the future using high-resolution neutron diffraction, which is outside the scope of the present work.

Refined lattice parameters for all samples of M -YbTaO₄ from different synthesis runs are highly consistent, demonstrating that this synthesis route is repeatable and reliable (see table in the Supplemental Material [35]). The crystal structure of M -YbTaO₄ is built up from second-order Jahn-Teller distorted TaO₆ octahedra [41], as shown in Fig. 1, and YbO₈ polyhedra, which are best described as distorted square antiprisms with the unique direction along the c axis [26]. These polyhedra are linked together by edges and vertices to form the crystal structure with its two interlocking “stretched diamond” networks, one for the magnetic Yb³⁺ and one for the nonmagnetic Ta⁵⁺. M -YbTaO₄ is isostructural with YbNbO₄, which has been recently investigated by Kumar *et al.* [25].

We also synthesized several samples from the solid solution YbNb _{x} Ta_{1- x} O₄, $0 \leq x \leq 1$. At ambient pressure, only the M phase formed in the Nb-rich samples with $x \geq 0.5$; only

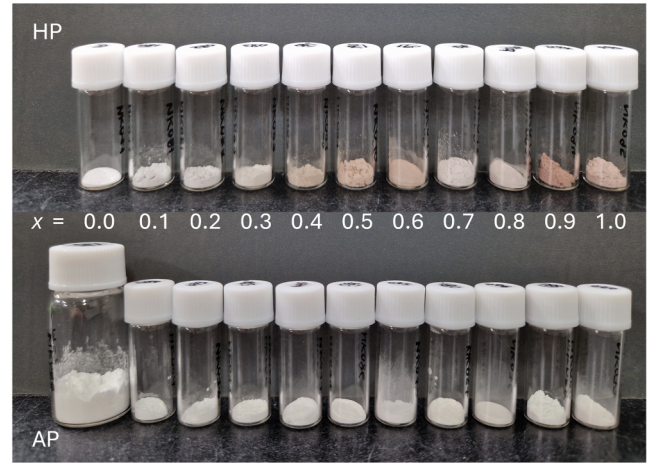
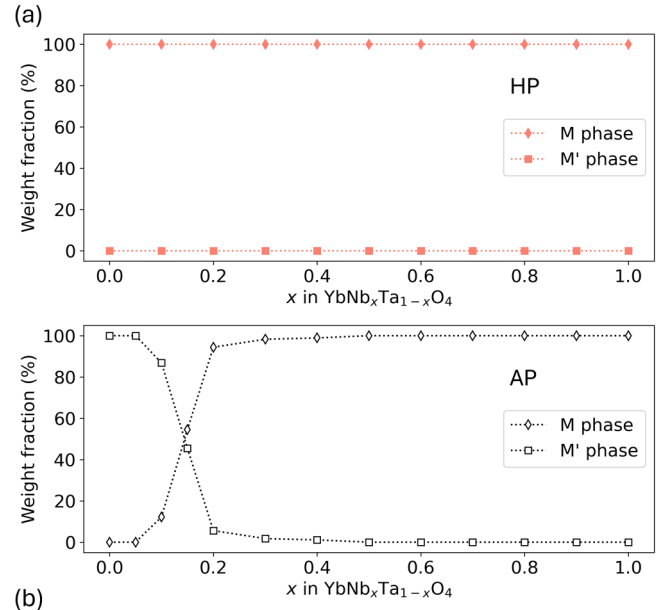


FIG. 4. (a) Refined weight fractions of the M and M' phases of YbNb _{x} Ta_{1- x} O₄ made through high-pressure (HP, top) versus ambient-pressure synthesis (AP, bottom). (b) Pictures of samples show the different colors observed under different synthetic conditions.

the M' phase formed for the Ta-rich samples $x \leq 0.05$; while at intermediate values $0.1 \leq x \leq 0.4$ a mixture of both phases was observed; see Fig. 4. Our data are consistent with the previous findings of Mullens *et al.*, whose ambient-pressure synthesis at 1400 °C gave only the M' phase for YbTaO₄, only M for YbNb_{0.4}Ta_{0.6}O₄ and more Nb-rich compositions, and a phase mixture for YbNb_{0.2}Ta_{0.8}O₄ [42]. In contrast, under our high-pressure conditions (6 GPa, 1800 °C, 1 h) only the M phase was observed for all x . However, many of the high-pressure samples with $x \neq 0$ were beige in color, rather than white like the whole ambient-pressure series (Fig. 4). No impurities or structural transformations were visible by powder x-ray diffraction (additional Rietveld refinements available in the Supplemental Material [35]) to explain the color, which also did not seem to follow a clear trend with x . Furthermore, the lattice parameters were broadly consistent between the two synthesis methods, Fig. 5(a), within experimental error.

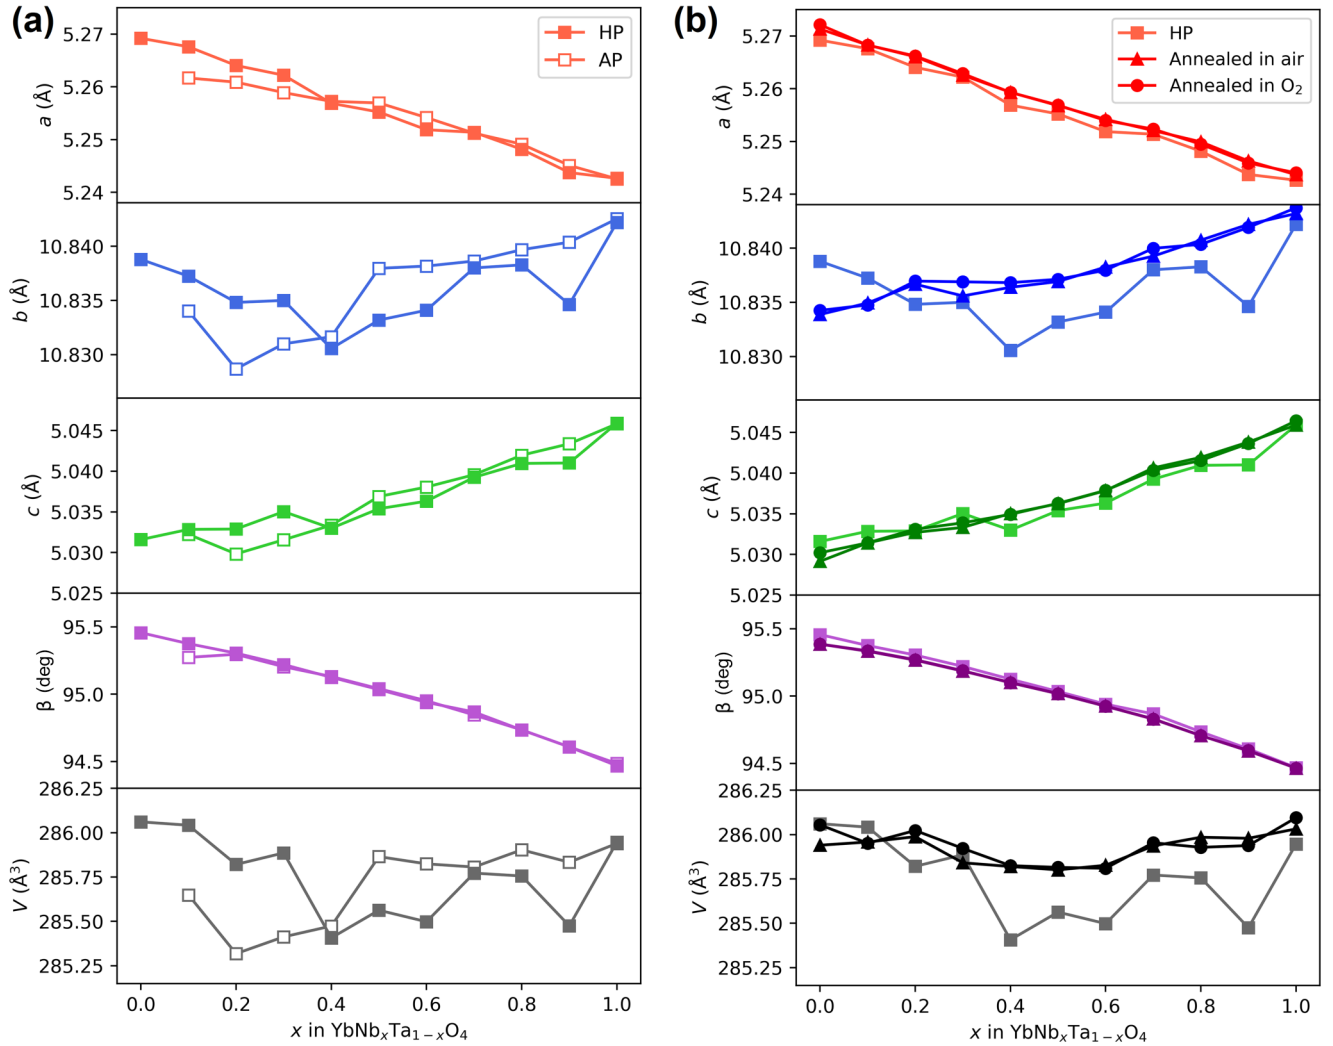


FIG. 5. Refined unit cell parameters of the compounds $\text{YbNb}_x\text{Ta}_{1-x}\text{O}_4$ (M -type crystal structure) as a function of x . (a) Comparison of samples made by high-pressure (HP) and ambient-pressure (AP) synthesis. (b) Comparison of the HP samples as-synthesized and after annealing in either air or pure oxygen. Error bars are smaller than the data points in all cases.

The color of the high-pressure samples might arise from charge transfer behavior, i.e., promotion of electrons from ligands (oxide ions) into the unfilled Yb $4f$ shell to form localized Yb^{2+} ions [44]. However, we also note that off-stoichiometry in the pyrochlore oxide $\text{Yb}_{2+x}\text{Ti}_{2-x}\text{O}_{7-\delta}$ has been found to have a significant impact on the color of single-crystal samples, even where oxygen vacancies can account for all Yb ions remaining in the $+3$ state [45]. In fact, refining the metal cation site occupancies in our samples gave no indication of off-stoichiometry. Alternatively, other defects such as nitrogen impurity centers may be present and/or the formation of some Yb^{2+} ions might be compensated by vacancies formed in the oxide-ion sublattice under high-pressure-high-temperature synthesis, which is known to alter the patterns of defects and optical centers in doped gemstones [46].

In order to investigate potential variation in the oxide stoichiometry, portions of the samples made under high pressure were subsequently annealed for 2 h at 800°C in a chamber furnace under static air atmosphere or in a tube furnace under flowing O_2 gas. After removal from the furnaces, all samples had changed to a pure white color (images available in the

Supplemental Material [35]). PXRD measurements, Fig. 5(b), showed that the samples annealed in air and in O_2 were identical to each other and their lattice parameters were very close to the as-made samples, indicating that there was no structural transition. Overall, the trends with x , particularly the trend in b , became smoother after annealing. The low scattering power of oxygen meant that the oxygen site occupancies could not be refined. However, these observations suggest that the observed color change upon annealing is related to a change in the oxide ion composition and/or the oxidation of isolated Yb^{2+} ions. The presence of Yb^{2+} ions in the as-made samples would be possible because of the slightly reducing synthetic environment of the high-pressure apparatus (Pt capsule surrounded by graphite).

B. Magnetic measurements

Magnetic susceptibility measurements were carried out on several samples of M - YbTaO_4 (as-made after HP synthesis). The presence of nonmagnetic PtO up to about 5 wt.%, as mentioned in Sec. III A, was quantified by Rietveld refinement

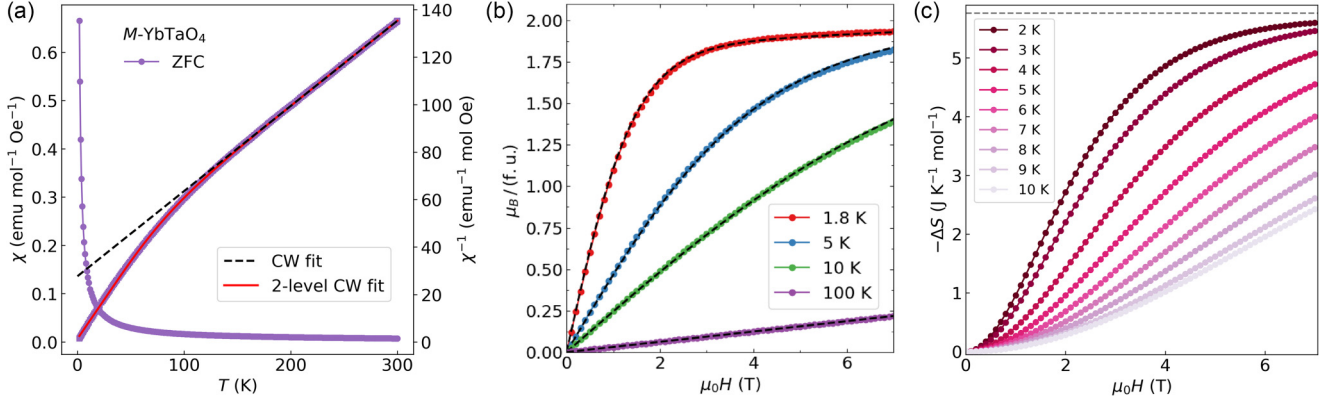


FIG. 6. Magnetic data for a sample of $M\text{-YbTaO}_4$ (NK099): (a) magnetic susceptibility $\chi(T)$ and inverse susceptibility $\chi^{-1}(T)$. The inverse susceptibility was fitted to a simple Curie-Weiss law (black dashed line, extrapolated from 150 down to 0 K) or a modified two-level Curie-Weiss law to account for crystal electric field effects (red solid line). (b) Isothermal magnetization curves, fitted to the Brillouin function with $J = \frac{1}{2}$ (black dashed lines). (c) Magnetocaloric effect calculated from magnetic isotherms. The gray dashed line shows the expected maximum value of $-\Delta S = R \ln 2$.

[35] in order to correct the raw data. The susceptibility is given by $\chi \approx M/H$ because H is small (500 Oe) and $M(H)$ is linear in this region. No magnetic ordering was observed in any of the samples down to a minimum temperature of 1.8 K and the ZFC and FC curves were identical (Supplemental Material [35]), which rules out any spin-glass behavior in this temperature range. A representative data set is shown in Fig. 6(a) and fitted parameters for all samples are tabulated in the Supplemental Material [35].

The inverse susceptibility, $\chi^{-1}(T)$, was first fitted to the Curie-Weiss (CW) law:

$$\frac{1}{\chi} = \frac{8(T - \theta_{CW})}{\mu_{eff}^2}, \quad (2)$$

where θ_{CW} is the Weiss temperature and μ_{eff} the effective magnetic moment. Linear fitting in the range 150–300 K, on average for several samples of $M\text{-YbTaO}_4$, yielded $\theta_{CW} = -78(7)$ K and $\mu_{eff} = 4.79(11)\mu_B$ [black dashed line in Fig. 6(a)]. While the effective moment is close to the estimated free-ion value for Yb^{3+} ions, $4.54\mu_B$, the Weiss temperature is unphysically large for the expected strength of magnetic exchange interactions, which is typically of the order of 1–10 K for lanthanide compounds. Similarly large estimates of the Weiss temperature have been observed for other Yb compounds and the unsuitability of the simple Curie-Weiss model is explained by contributions from thermally populated crystal electric field (CEF) levels above the $J = \frac{7}{2}$ ground state; a low-temperature Curie-Weiss fit is often used to mitigate this [47,48]. However, Yb^{3+} is a Kramers ion (with an odd number of unpaired electrons) so its $J = \frac{7}{2}$ state is expected to split into four doublets, with the ground state being a $J = \pm\frac{1}{2}$ doublet, separated from the first excited state (a $J = \pm\frac{3}{2}$ doublet) by an energy gap ΔE_{10} . Therefore, we fitted the data in the entire temperature range (1.8–300 K) to a two-level function:

$$\frac{1}{\chi} = 8(T - \theta_{CW}) \left(\frac{1 + e^{-\Delta E_{10}/k_B T}}{\mu_0^2 + \mu_1^2 e^{-\Delta E_{10}/k_B T}} \right), \quad (3)$$

where μ_0 is the effective magnetic moment in the ground state, μ_1 the effective moment in the first excited state, and

ΔE_{10} the energy difference between those states [49]. The two-level fitting [red solid line in Fig. 6(a)] was carried out for eleven distinct $M\text{-YbTaO}_4$ samples from different synthesis runs (tabulated in the Supplemental Material [35]). The fitted parameters, on average over all the samples, were $\theta_{CW} = -2.4(6)$ K, $\Delta E_{10} = 256(16)$ K, $\mu_0 = 3.48(8)\mu_B$, and $\mu_1 = 5.8(3)\mu_B$. The negative Weiss temperature indicates antiferromagnetic interactions in $M\text{-YbTaO}_4$ and the sizes of the effective moments are in line with those obtained in other Yb-based metal oxides using the same fitting model [25,28,50]. We also fitted the susceptibility to the CW law in the low-temperature regime, $1.8 \leq T(\text{K}) \leq 30$, which resulted in $\theta_{CW}^{LT} = -0.68(14)$ K and $\mu_{eff}^{LT} = 3.32(8)\mu_B$. The obtained low-temperature effective moment is clearly reduced compared with the high-temperature effective moment and, importantly, it is consistent with μ_0 obtained from the two-level CW fitting, indicating that the two-level $J_{eff} = \frac{1}{2}$ model is a good fit for our data.

Isothermal magnetization data collected on $M\text{-YbTaO}_4$ as a function of field are shown in Fig. 6(b). The magnetization approached saturation at low temperatures and high fields. The data at 1.8 K were first fitted to a linear function in the range 5–7 T, representing the temperature-independent paramagnetism [51]. This yielded a gradient $\chi_0 = 1.5(2) \times 10^{-2}$ emu mol⁻¹ and intercept (saturation magnetization) $\mu_{sat} = 1.82(6)\mu_B$. The g factor could then be estimated using $g_{eff} = (\mu_{sat}/\mu_B)/J_{eff}$ [52] = 3.65(12) for $J_{eff} = \frac{1}{2}$.

Next, the data sets at each temperature T were fitted in the entire field range to the function

$$M(H) = \chi_0 H + g J B_J(H), \quad (4)$$

where g is the Landé g factor and $B_J(H)$ the Brillouin function. For an effective $J = \frac{1}{2}$, typical of Yb^{3+} compounds, the Brillouin function is given by $B_J(H) = \tanh(\frac{gJ\mu_B H}{k_B T})$. The fits are shown in Fig. 6(b) as black dashed lines. The fitted g factor at 1.8 K was $g = 3.58(8)$, which is consistent with our earlier estimate and comparable with those of NaYbGeO_4 (3.84) [52], $M'\text{-YbTaO}_4$ (3.2) [28], YbNbO_4 (3.0) [25], and $\text{Na}_{0.5}\text{Yb}_{0.5}\text{WO}_4$ (3.1) [50]. The saturation magnetization M_{sat} ,

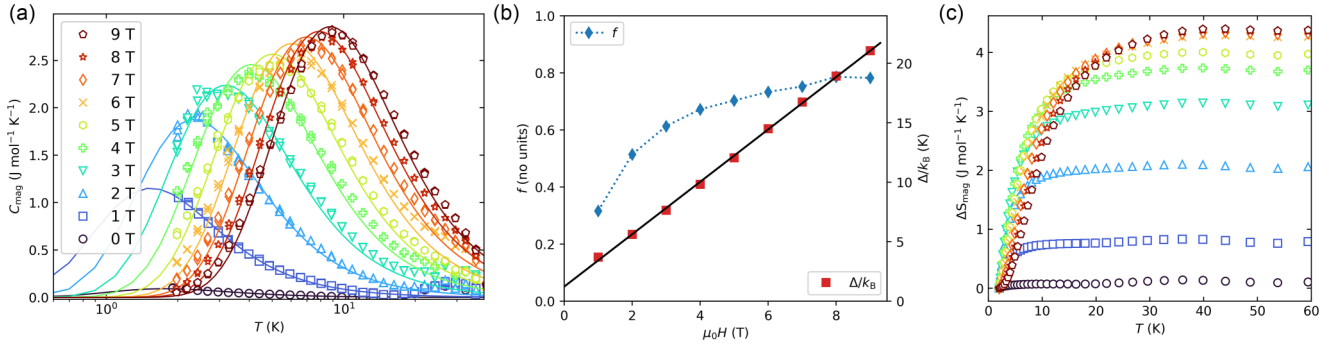


FIG. 7. (a) Magnetic specific heat C_{mag} for $M\text{-YbTaO}_4$ at different applied fields, fitted to the two-level Schottky equation. (b) Fitted parameters f and Δ/k_B as a function of field. (c) Magnetic entropy change obtained by integration of C_{mag}/T ; for the legend, see part (a).

estimated by extrapolating the high-field linear region of $M(H)$ back to zero field, was $1.82(6)\mu_B$. Comparing this value with $g_J \cdot J = 4$ for the Yb^{3+} ion indicates substantial single-ion anisotropy, most likely Ising-like because $M_{\text{sat}} \approx g_J \cdot J/2$ [53].

We also calculated the magnetocaloric effect (MCE) from evenly spaced magnetic isotherms (with data points at 1 K intervals from 2 to 10 K and 1000 Oe intervals from 0 to 7 T) using Maxwell's relations [54]. We found a maximum MCE of $-\Delta S_{\text{mag}}(2 \text{ K}, 7 \text{ T}) = 5.60 \text{ J mol}^{-1} \text{K}^{-1}$, which is almost equal to $R \ln 2 = 5.76 \text{ J mol}^{-1} \text{K}^{-1}$; see Fig. 6(c). This indicates that the effective quantum number $J_{\text{eff}} = \frac{1}{2}$ is appropriate for $M\text{-YbTaO}_4$, as for a number of other Yb-based oxides [25,28,29,50,52].

Magnetic susceptibility and isothermal magnetization data were also collected on all samples from the solid solution $\text{YbNb}_x\text{Ta}_{1-x}\text{O}_4$ after annealing in oxygen (see Sec. III A) and on several other samples either as-made or annealed in air. Two-level Curie-Weiss fits to the susceptibility were carried out in the same manner as described above. The fitted magnetic parameters (Supplemental Material [35]) showed no obvious trends as a function of x and the spread of data for each parameter was of a similar magnitude to the uncertainties reported above, which were obtained by averaging over several samples of the same composition. Therefore, we cannot draw any conclusions from this data set about the effect of Nb substitution on the magnetic properties of $M\text{-YbTaO}_4$.

C. Specific heat

Specific heat data were collected on $M\text{-YbTaO}_4$ at several fields in the temperature range 2–60 K and fitted to the Debye law with $\theta_D = 246(2) \text{ K}$ in order to provide an estimate of the lattice contribution to the specific heat, C_{latt} , which was then subtracted to give the magnetic contribution C_{mag} . Figure 7(a) shows C_{mag} for all fields. In nonzero applied fields a broad Schottky-type anomaly is visible, shifting to higher temperatures as the field increases. This behavior is consistent with Zeeman splitting of a $J = \frac{1}{2}$ doublet [51]. The C_{mag} curves were fitted to a two-level Schottky function:

$$C_S(T, H) = fR \left(\frac{\Delta}{k_B T} \right)^2 \frac{e^{\Delta/k_B T}}{(e^{\Delta/k_B T} + 1)^2}, \quad (5)$$

where f is the molar fraction of free spins, R the molar gas constant, and Δ the Zeeman energy gap in the split ground

state doublet. The model fits our data well, as shown by the solid lines in Fig. 7(a). The gap Δ increases linearly with field as expected, with f also increasing but not reaching 100% by $\mu_0 H = 9 \text{ T}$; see Fig. 7(b). Extrapolation of the straight-line fit of $\Delta(H)$ indicates a small finite energy gap at zero field, $\Delta(0) \approx 1.2 \text{ K}$, which may correspond to interactions between Yb^{3+} ions, but is well below the minimum temperature of the present work. Further measurements at $T < 2 \text{ K}$ will be important for future investigation of $M\text{-YbTaO}_4$.

The magnetic entropy, ΔS_{mag} , was obtained by integrating C_{mag}/T and is shown in Fig. 7(c). At high fields the entropy saturates at $4.38 \text{ J mol}^{-1} \text{K}^{-1}$, which is around three-quarters of the expected value of $R \ln 2 = 5.76 \text{ J mol}^{-1} \text{K}^{-1}$ for a two-level system. Since we found that the magnetic entropy change reached almost $R \ln 2$ in our MCE calculation [Fig. 6(c)], this is probably a systematic offset with the “missing” entropy being gained below 2 K, because the starting point for our numerical integration of C_{mag}/T was $T = 2 \text{ K}$ instead of the ideal value of zero.

IV. DISCUSSION

The lanthanide niobates and tantalates exhibit several different structural polymorphs including at least one tetragonal and three monoclinic phases, depending on the transition metal ion (Nb vs Ta), lanthanide ion, temperature, and pressure [42]. Of these, the M or fergusonite-type monoclinic phase is of particular interest for its stretched diamond network of magnetic ions, which has previously been studied in both the niobates [25] and tantalates [23,24]. While antiferromagnetically coupled spins on a cubic diamond lattice are expected to display long-range magnetic order, lowering of symmetry to tetragonal or monoclinic crystal structures typically introduces magnetic frustration due to competing interactions. Additional complexity is possible in the case of nonmagnetic substitution onto the diamond-like lattice, for example, in $\text{Na}_{0.5}\text{Yb}_{0.5}\text{WO}_4$ with 50:50 random site occupancy of Na^+ and Yb^{3+} [50].

$M\text{-YbTaO}_4$ is an example of a monoclinic stretched diamond lattice with no site disorder. Like its niobate analog YbNbO_4 [25], we observed evidence for a $J_{\text{eff}} = \frac{1}{2}$ Kramers doublet down to 1.8 K in the analysis of susceptibility, isothermal magnetization, and specific heat data. Kramers behavior is typical of compounds containing the Yb^{3+} ion, which has a half-integer spin and strong spin-orbit coupling, in a

low-symmetry crystal electric field environment such as the distorted YbO_8 polyhedra of $M\text{-YbTaO}_4$. In such compounds, the $J_{\text{eff}} = \frac{1}{2}$ ground state means that the effective magnetic moment at low temperatures is smaller than expected. Indeed, the susceptibility data for $M\text{-YbTaO}_4$ clearly showed that the Curie-Weiss law does not hold over the entire temperature range studied (1.8–300 K), i.e., the effective magnetic moment is strongly temperature dependent. We calculated $\theta_{\text{CW}}^{\text{LT}} = -0.68(14)$ K, which suggests that the exchange interactions between neighboring Yb^{3+} ions are very weak. The nearest-neighbor interaction strength J_{nn} , in the mean-field limit, may be estimated as follows [55]:

$$J_{\text{nn}} \approx \frac{3k_B\theta_{\text{CW}}}{2zS(S+1)}. \quad (6)$$

Substituting $J_{\text{eff}} = \frac{1}{2}$ for the spin quantum number S , and setting the number of neighboring ions $z = 4$, we obtain an estimated $J_{\text{nn}} \approx -0.34$ K using $\theta_{\text{CW}}^{\text{LT}}$. We can also estimate the dipolar interaction, $D = -\mu_0\mu_{\text{eff}}^2/4\pi r^3$, where r is the (average) nearest-neighbor distance and $\mu_0 = 4\pi \times 10^{-7}$ is the permeability of free space [56]. Each Yb^{3+} ion in $M\text{-YbTaO}_4$ has four neighboring Yb^{3+} ions, two at a distance of 3.691(4) Å and two at a distance of 3.791(4) Å according to our Rietveld refinements (at room temperature). Taking the average as $r \approx 3.741$ Å, we calculate $D \approx -0.29$ K, which is a similar size to J_{nn} . However, these mean-field approximations do not take spin anisotropy into account, whereas our $M(H)$ data indicate substantial anisotropy for the Yb^{3+} ions. Both of the estimated values are considerably smaller than 1.8 K, so the effects of the interplay between dipolar and exchange coupling will only be observed at temperatures below the minimum achieved in this experimental study.

Magnetocaloric calculations for $M\text{-YbTaO}_4$ indicate that the magnetic entropy change is more than 97% of the maximum ($R \ln 2$) at 2 K and 7 T. This result, coupled with the weak magnetic exchange and geometric frustration which should act to suppress magnetic ordering, means that $M\text{-YbTaO}_4$ has the potential to be used as a magnetocaloric material in adiabatic demagnetization refrigerators (ADRs) at liquid-helium or dilution temperatures. ADRs have traditionally used single crystals of paramagnetic salts, but these often contain water of crystallization and therefore cannot be evacuated or heated above 100 °C in preparation for ultrahigh vacuum applications. However, recent studies have found that some chemically stable ytterbium-based oxides are strong contenders for new ADR technology [52,57,58]. The ADR technique itself can even be used to determine magnetic transition temperatures, using an indirect measurement of heat capacity calculated from the heat input and the time derivative of the measured temperature [52]. The experimental setup for such a measurement usually requires at least 2 g of the sample, which would necessitate the combination of several 0.5 g samples from different high-pressure synthesis runs. However, our results show that this synthesis route is repeatable and produces samples with consistent structural and magnetic parameters, so there is potential for $M\text{-YbTaO}_4$ to be investigated for ADR applications in the near future.

Finally, we compare $M\text{-YbTaO}_4$ with the niobate YbNbO_4 . The two compounds have almost identical unit cell dimensions, less than 0.05% difference in unit cell volume, because

TABLE II. Comparison of fitted magnetic parameters for $M\text{-YbTaO}_4$ (this work) and the isostructural YbNbO_4 [25].

	$M\text{-YbTaO}_4$ (This work)	YbNbO_4 [25]
High-temperature fitting		
θ_{CW} (K)	−78(7)	−113(5)
μ_{eff} (μ_B)	4.79(11)	4.59(14)
Low-temperature fitting		
θ_{CW} (K)	−0.68(14)	0.025
μ_{eff} (μ_B)	3.32(8)	2.68(18)
Two-level fitting		
θ_{CW} (K)	−2.4(6)	−9.40
μ_0 (μ_B)	3.48(8)	3.40
μ_1 (μ_B)	5.8(3)	6.45
ΔE_{10} (K)	256(16)	330
g from $\chi(T)$	3.65(12)	3.1
g from $M(H)$ at 1.8 K	3.58(8)	3.0
M_{sat} at 1.8 K (μ_B)	1.82(6)	1.48

Nb^{5+} and Ta^{5+} have identical ionic radii (0.64 Å if six-coordinate [43]). Given the very similar ionic radii, it is perhaps surprising that high temperature and/or pressure (depending on Ln) is required to stabilize M over M' for the lanthanide tantalates while the niobates do not display the M' phase at all. The $\text{HoTaO}_4\text{-HoNbO}_4$ solid solution has recently been explored in depth using a combined synchrotron x-ray and neutron diffraction study [42]. The authors found subtle differences in the (Nb/Ta)–O bond lengths which could be related to the natures of the valence orbitals (4d vs 5d), with Ta–O bonds having greater covalency than Nb–O bonds. The transition metal ions were also more displaced from the centers of the (Nb/Ta) O_6 polyhedra in the Ta-rich samples, which were described as a second-order Jahn-Teller effect. Since the phase behavior of $Ln(\text{Nb/Ta})\text{O}_4$ compounds depends strongly on the Ln ion [26,27], and oxide ions are weak scatterers of x rays, we plan to carry out neutron diffraction studies on our Yb samples in order to locate the oxide ions accurately and explore this further.

YbNbO_4 , recently investigated by Kumar *et al.*, also has a $J_{\text{eff}} = \frac{1}{2}$ Kramers doublet ground state with temperature-dependent effective magnetic moment. The magnetic parameters of $M\text{-YbTaO}_4$ and YbNbO_4 are compared in Table II. In YbNbO_4 , muon-spin relaxation (μSR) data at low temperatures demonstrated strong magnetic correlations in a dynamic internal field with no ordering or freezing of spins down to 300 mK, making it a strong candidate for quantum spin liquid properties [25]. Our results at $T \geq 1.8$ K suggest that $M\text{-YbTaO}_4$ would also benefit from μSR and/or neutron diffraction measurements at low temperatures to rule out long- or short-range magnetic order and inelastic scattering at higher temperatures to investigate the crystal electric field levels and confirm the size of the energy gap between the ground and excited state doublets. Further specific heat and ac susceptibility experiments below 1.8 K are also planned.

V. CONCLUSIONS

We synthesized $M\text{-YbTaO}_4$, which can only be produced under high-pressure-high-temperature conditions, and

measured its bulk magnetic properties. Similarly to its niobate analog, which also hosts a stretched diamond lattice of Yb^{3+} spins, no magnetic ordering or spin freezing is observed down to a minimum temperature of 1.8 K. Analysis of specific heat data provides evidence for a $J_{\text{eff}} = \frac{1}{2}$ Kramers doublet state down to 1.8 K, which splits upon application of an external magnetic field. This conclusion is further supported by analysis of the low-temperature magnetic susceptibility, magnetic isotherms, and magnetocaloric calculations.

In the solid solution $\text{YbNb}_x\text{Ta}_{1-x}\text{O}_4$, the application of pressure is required at $x \leq 0.1$ to stabilize the M phase at all and at $x \leq 0.4$ to obtain only the M phase. Under conditions of 1800 °C and 6 GPa, the competing M' phase is completely suppressed for all x . However, an interesting variation in color across the series of high-pressure samples was observed and ascribed to off-stoichiometry, pointing to subtle differences in the crystal chemistry which should be investigated further using high-resolution diffraction techniques and optical measurements.

Overall, this study has explored a new material example of spin- $\frac{1}{2}$ magnetism on a diamond-like lattice, synthesized in a practical high-pressure synthesis window with high reproducibility. M - YbTaO_4 has possible future applications in ADR technology, owing to its chemical stability and lack of magnetic ordering above 1.8 K, and has a high potential for unusual quantum magnetism to be observed at low temperatures in future studies.

ACKNOWLEDGMENTS

We acknowledge funding from Jesus College, Cambridge for a Research Fellowship, from the EPSRC for the use of the Advanced Materials Characterisation Suite (Grant No. EP/M000524/1), and from the Japan Society for the Promotion of Science (JSPS) under the Summer Program International Research fellowship (No. SP25116) and KAKENHI Grants-in-Aid for Scientific Research (No. 25K01507 and No. 25K01657). Part of this work was supported by “Advanced Research Infrastructure for Materials and Nanotechnology in Japan (ARIM)” of the Ministry of Education, Culture, Sports, Science and Technology (MEXT), Proposal No. JPMXP1225NM5105.

The authors contributed to the work as follows. N.D.K.: conceptualization, funding acquisition, investigation, formal analysis, visualization, and writing—original draft. X.L.: investigation and writing—review and editing. S.E.D.: conceptualization, resources, supervision, and writing—review and editing. K.Y.: funding acquisition, resources, and writing—review and editing. Y.T.: funding acquisition, resources, supervision, and writing—review and editing.

DATA AVAILABILITY

The data that support the findings of this article are openly available [59].

- [1] H. Huppertz, Multianvil high-pressure synthesis and crystal structure of β - YbBO_3 , *Z. Naturforsch. B: Chem. Sci.* **56**, 697 (2001).
- [2] H. Huppertz, B. von der Eltz, R. D. Hoffmann, and H. Piotrowski, Multianvil high-pressure syntheses and crystal structures of the new rare-earth oxoborates χ - DyBO_3 and χ - ErBO_3 , *J. Solid State Chem.* **166**, 203 (2002).
- [3] H. Emme and H. Huppertz, High-pressure synthesis of ν - DyBO_3 , *Acta Crystallogr. Sect. C: Cryst. Struct. Commun.* **60**, i117 (2004).
- [4] S.-J. Song, Y.-Q. Lin, B.-Z. Li, S.-Q. Wu, Q.-Q. Zhu, Z. Ren, and G.-H. Cao, Tetragonal polymorph of $\text{BaFe}_2\text{S}_2\text{O}$ as an antiferromagnetic Mott insulator, *Phys. Rev. Mater.* **6**, 055002 (2022).
- [5] F. Takeiri, Y. Matsumoto, T. Yamamoto, N. Hayashi, Z. Li, T. Tohyama, C. Tassel, C. Ritter, Y. Narumi, M. Hagiwara, and H. Kageyama, High-pressure synthesis of the layered iron oxytelluride $\text{BaFe}_2\text{Se}_2\text{O}$ with strong magnetic anisotropy, *Phys. Rev. B* **94**, 184426 (2016).
- [6] Y. Tsujimoto, J. Sugiyama, M. Ochi, K. Kuroki, P. Manuel, D. D. Khalyavin, I. Umegaki, M. Månsson, D. Andreica, S. Hara, T. Sakurai, S. Okubo, H. Ohta, A. T. Boothroyd, and K. Yamaura, Impact of mixed anion ordered state on the magnetic ground states of $S = 1/2$ square-lattice quantum spin antiferromagnets, $\text{Sr}_2\text{NiO}_3\text{Cl}$ and $\text{Sr}_2\text{NiO}_3\text{F}$, *Phys. Rev. Mater.* **6**, 114404 (2022).
- [7] Y. Yuan, M. Yang, S. D. Kloss, and J. P. Attfield, A new family of high oxidation state antiperovskite nitrides: La_3MN_5 ($M = \text{Cr}$, Mn and Mo), *Angew. Chem. Int. Ed.* **63**, e202405498 (2024).
- [8] M. Markkula, A. M. Arévalo-López, A. Kusmartseva, J. A. Rodgers, C. Ritter, H. Wu, and J. P. Attfield, Incommensurate spin order in the metallic perovskite MnVO_3 , *Phys. Rev. B* **84**, 094450 (2011).
- [9] A. Almadhi, K. Ji, S. D. Injac, C. Ritter, and J. P. Attfield, $(\text{Ca}_{0.5}\text{Mn}_{0.5})_2\text{MnTeO}_6$ – An anomalously stable high-pressure double perovskite, *Chem. Asian J.* **19**, e202400280 (2024).
- [10] E.-P. Liu, S. M. Kumawat, C.-C. Lee, T.-H. Liu, A. M. Arévalo-López, W.-T. Chen, and C.-L. Huang, Complex magnetic properties of the double perovskite $\text{Hg}_2\text{MnTeO}_6$ probed by thermodynamic measurements and neutron diffraction, *Phys. Rev. B* **112**, 104436 (2025).
- [11] E. Solana-Madruga, C. Ritter, C. Aguilar-Maldonado, O. Mentré, J. P. Attfield, and A. M. Arévalo-López, $\text{Mn}_3\text{MnNb}_2\text{O}_9$: High-pressure triple perovskite with 1:2 B-site order and modulated spins, *Chem. Commun.* **57**, 8441 (2021).
- [12] X. Liang, K. Yamaura, and A. A. Belik, Cryogenic magnetocaloric properties of zinc-based perovskite $\text{Nd}_2\text{ZnZn}(\text{Zn}_2\text{Sb}_2)\text{O}_{12}$ with A-site columnar-type and B-site rock-salt-type orders, *Acta Mater.* **302**, 121626 (2026).
- [13] N. Tristan, J. Hemberger, A. Krimmel, H. A. K. von Nidda, V. Tsurkan, and A. Loidl, Geometric frustration in the cubic spinels $M\text{Al}_2\text{O}_4$ ($M = \text{Co}$, Fe , and Mn), *Phys. Rev. B* **72**, 174404 (2005).
- [14] L. Ge, J. Flynn, J. A. M. Paddison, M. B. Stone, S. Calder, M. A. Subramanian, A. P. Ramirez, and M. Mourigal, Spin order and dynamics in the diamond-lattice Heisenberg antiferromagnets CuRh_2O_4 and CoRh_2O_4 , *Phys. Rev. B* **96**, 064413 (2017).

- [15] V. Fritsch, J. Hemberger, N. Büttgen, E.-W. Scheidt, H.-A. Krug von Nidda, A. Loidl, and V. Tsurkan, Spin and orbital frustration in MnSc_2S_4 and FeSc_2S_4 , *Phys. Rev. Lett.* **92**, 116401 (2004).
- [16] H. Cho, R. Nirmala, J. Jeong, P. J. Baker, H. Takeda, N. Mera, S. J. Blundell, M. Takigawa, D. T. Adroja, and J.-G. Park, Dynamic spin fluctuations in the frustrated a -site spinel CuAl_2O_4 , *Phys. Rev. B* **102**, 014439 (2020).
- [17] M. M. Bordelon, C. Liu, L. Posthuma, E. Kenney, M. J. Graf, N. P. Butch, A. Banerjee, S. Calder, L. Balents, and S. D. Wilson, Frustrated Heisenberg $J_1 - J_2$ model within the stretched diamond lattice of LiYbO_2 , *Phys. Rev. B* **103**, 014420 (2021).
- [18] A. H. Abdeldaim, T. Li, L. Farrar, A. A. Tsirlin, W. Yao, A. S. Gibbs, P. Manuel, P. Lightfoot, G. J. Nilsen, and L. Clark, Realising square and diamond lattice $S = 1/2$ Heisenberg antiferromagnet models in the α and β phases of the coordination framework, $\text{KTi}(\text{C}_2\text{O}_4)_2 \cdot x\text{H}_2\text{O}$, *Phys. Rev. Mater.* **4**, 104414 (2020).
- [19] C. A. Marjerrison, C. Mauws, A. Z. Sharma, C. R. Wiebe, S. Derakhshan, C. Boyer, B. D. Gaulin, and J. E. Greedan, Structure and magnetic properties of KRuO_4 , *Inorg. Chem.* **55**, 12897 (2016).
- [20] J. R. Chamorro, L. Ge, J. Flynn, M. A. Subramanian, M. Mourigal, and T. M. McQueen, Frustrated spin one on a diamond lattice in NiRh_2O_4 , *Phys. Rev. Mater.* **2**, 034404 (2018).
- [21] M. M. Bordelon, J. D. Bocarsly, L. Posthuma, A. Banerjee, Q. Zhang, and S. D. Wilson, Antiferromagnetism and crystalline-electric field excitations in tetragonal NaCeO_2 , *Phys. Rev. B* **103**, 024430 (2021).
- [22] P. Mukherjee, E. Suard, and S. E. Dutton, Magnetic properties of monoclinic lanthanide metaborates, $\text{Ln}(\text{BO}_2)_3$, $\text{Ln} = \text{Pr}, \text{Nd}, \text{Gd}, \text{Tb}$, *J. Phys.: Condens. Matter* **29**, 405807 (2017).
- [23] N. D. Kelly, L. Yuan, R. L. Pearson, E. Suard, I. P. Orench, and S. E. Dutton, Magnetism on the stretched diamond lattice in lanthanide orthotantalates, *Phys. Rev. Mater.* **6**, 044410 (2022).
- [24] X. Zhang, N. D. Kelly, D. Sheptyakov, C. Liu, S. Deng, S. S. Saxena, and S. E. Dutton, Magnetoelastic coupling in the stretched diamond lattice of TbTaO_4 , *Mater. Adv.* **6**, 2570 (2025).
- [25] J. Kumar, D. Ranaut, J. G. Nakamura, and K. Mukherjee, Presence of a correlated dynamical ground state in the stretched diamond lattice system YbNbO_4 , *Phys. Rev. B* **111**, 014411 (2025).
- [26] L. H. Brixner and H. Y. Chen, On the structural and luminescent properties of the $\text{M}' \text{LnTaO}_4$ rare earth tantalates, *J. Electrochem. Soc.* **130**, 2435 (1983).
- [27] V. Y. Markiv, N. M. Belyavina, M. V. Markiv, Y. Titov, A. M. Sych, A. N. Sokolov, A. A. Kapshuk, and M. S. Slobodyanyk, Peculiarities of polymorphic transformations in YbTaO_4 and crystal structure of its modifications, *J. Alloys Compd.* **346**, 263 (2002).
- [28] J. Kumar, R. Roy, D. Ranaut, J. G. Nakamura, S. Kanungo, and K. Mukherjee, YbTaO_4 : A quasi-two-dimensional frustrated magnet possessing spin orbit entangled Kramers doublet ground state, *Phys. Rev. B* **110**, 174420 (2024).
- [29] A. Ramanathan, M. Mourigal, and H. S. La Pierre, Frustrated magnetism and spin anisotropy in a buckled square net YbTaO_4 , *Inorg. Chem.* **64**, 158 (2025).
- [30] H. T. Hall, Ultra-high-pressure, high-temperature apparatus: The “belt”, *Rev. Sci. Instrum.* **31**, 125 (1960).
- [31] M. Miyakawa and T. Taniguchi, Homogeneous heating of a sample space by a modified heating assembly in a belt-type high-pressure apparatus, *Rev. Sci. Instrum.* **86**, 025101 (2015).
- [32] H. M. Rietveld, A profile refinement method for nuclear and magnetic structures, *J. Appl. Crystallogr.* **2**, 65 (1969).
- [33] A. A. Coelho, TOPAS and TOPAS-Academic: An optimization program integrating computer algebra and crystallographic objects written in C++, *J. Appl. Crystallogr.* **51**, 210 (2018).
- [34] E. S. R. Gopal, *Specific Heats at Low Temperatures* (Springer US, Boston, MA, 1966).
- [35] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/3xqz-qzr7> for tables of synthesis attempts, photographs of annealed samples, and additional diffraction and magnetic data for the Nb-Ta solid solution.
- [36] C. Keller, Über ternäre oxide des niobs und tantals vom typ ABO_4 , *Z. Anorg. Allg. Chem.* **318**, 89 (1962).
- [37] A. D. Mighell, Conventional cells—The last step toward general acceptance of standard conventional cells for the reporting of crystallographic data, *J. Res. Natl. Inst. Stand. Technol.* **107**, 373 (2002).
- [38] B. A. Steele, E. Stavrou, J. C. Crowhurst, J. M. Zaug, V. B. Prakapenka, and I. I. Oleynik, High-pressure synthesis of a pentazolate salt, *Chem. Mater.* **29**, 735 (2017).
- [39] F. Xu, D. Yamazaki, N. Tsujino, and L. Guan, Lattice preferred orientation of stishovite deformed at high pressure and high temperature, *Phys. Earth Planet. Inter.* **306**, 106546 (2020).
- [40] S. L. Butler, J. F. Partridge, X. Huang, I. Suarez-Martinez, N. A. Marks, J. E. Bradby, and D. G. McCulloch, Origin of preferred orientation in an isotropic material: High pressure synthesis of bc8-Si , *Appl. Phys. Lett.* **123**, 231903 (2023).
- [41] M. Saura-Múzquiz, B. G. Mullens, H. E. Maynard-Casely, and B. J. Kennedy, Neutron diffraction study of the monoclinic-tetragonal phase transition in NdNbO_4 and NdTaO_4 , *Dalton Trans.* **50**, 11485 (2021).
- [42] B. G. Mullens, M. Saura-Múzquiz, F. P. Marlton, M. Avdeev, H. E. A. Brand, S. Mondal, G. Vaitheeswaran, and B. J. Kennedy, Beyond the ionic radii: A multifaceted approach to understand differences between the structures of LnNbO_4 and LnTaO_4 fergusonites, *J. Alloys Compd.* **930**, 167399 (2023).
- [43] R. D. Shannon, Revised effective ionic radii and systematic studies of interatomic distances in halides and chalcogenides, *Acta Crystallogr. A* **32**, 751 (1976).
- [44] E. Nakazawa, The lowest 4f-to-5d and charge-transfer transitions of rare earth ions in YPO_4 hosts, *J. Lumin.* **100**, 89 (2002).
- [45] K. E. Arpino, B. A. Trump, A. O. Scheie, T. M. McQueen, and S. M. Koohpayeh, Impact of stoichiometry of $\text{Yb}_2\text{Ti}_2\text{O}_7$ on its physical properties, *Phys. Rev. B* **95**, 094407 (2017).
- [46] V. V. Brazhkin, High-pressure synthesized materials: Treasures and hints, *High Press. Res.* **27**, 333 (2007).
- [47] F. Pan, S. Sun, A. I. Kolesnikov, M. B. Stone, J. Huang, D. Xu, C. Shang, B. Shi, X. Gui, Z. Sun, J. Wang, J. Liu, H. Zhang, Z. Liu, and P. Cheng, Structural and magnetic characterization of $\text{CeTa}_7\text{O}_{19}$ and $\text{YbTa}_7\text{O}_{19}$ triangular lattice, *Phys. Rev. B* **110**, 174448 (2024).
- [48] C. Y. Jiang, Y. X. Yang, Y. X. Gao, Z. T. Wan, Z. H. Zhu, T. Shiroka, C. S. Chen, Q. Wu, X. Li, J. C. Jiao, K. W. Chen, Y. Bao, Z. M. Tian, and L. Shu, Spin excitations in the quantum dipolar magnet $\text{Yb}(\text{BaBO}_3)_3$, *Phys. Rev. B* **106**, 014409 (2022).

- [49] S. Mugiraneza and A. M. Hallas, Tutorial: A beginner's guide to interpreting magnetic susceptibility data with the Curie-Weiss law, *Commun. Phys.* **5**, 95 (2022).
- [50] R. Kumar, A. G. Francis, R. Stewart, P. J. Baker, S. K. Pati, and A. Sundaresan, Quasiparamagnetic ground state in the hyperhoneycomb lattice compound $\text{Na}_{0.5}\text{Yb}_{0.5}\text{WO}_4$, *Phys. Rev. B* **111**, 094407 (2025).
- [51] S. Guchhait, R. Kolay, A. Magar, and R. Nath, Magnetic and crystal electric field studies of the Yb^{3+} -based triangular lattice antiferromagnets, *Phys. Rev. B* **111**, 214437 (2025).
- [52] U. Arjun, K. M. Ranjith, A. Jesche, F. Hirschberger, D. D. Sarma, and P. Gegenwart, Adiabatic demagnetization refrigeration to millikelvin temperatures with the distorted square lattice magnet NaYbGeO_4 , *Phys. Rev. B* **108**, 224415 (2023).
- [53] S. T. Bramwell, M. N. Field, M. J. Harris, and I. P. Parkin, Bulk magnetization of the heavy rare earth titanate pyrochlores - A series of model frustrated magnets, *J. Phys.: Condens. Matter* **12**, 483 (2000).
- [54] V. K. Pecharsky and K. A. Gschneidner, Magnetocaloric effect and magnetic refrigeration, *J. Magn. Magn. Mater.* **200**, 44 (1999).
- [55] A. P. Ramirez, Strongly geometrically frustrated magnets, *Annu. Rev. Mater. Sci.* **24**, 453 (1994).
- [56] M. J. P. Gingras, in *Introduction to Frustrated Magnetism*, edited by C. Lacroix, P. Mendels, and F. Mila, Springer Series in Solid State Science, Vol. 164 (Springer, Berlin Heidelberg, 2011).
- [57] Y. Tokiwa, S. Bachus, K. Kavita, A. Jesche, A. A. Tsirlin, and P. Gegenwart, Frustrated magnet for adiabatic demagnetization cooling to milli-Kelvin temperatures, *Commun. Mater.* **2**, 42 (2021).
- [58] U. Arjun, K. M. Ranjith, A. Jesche, F. Hirschberger, D. D. Sarma, and P. Gegenwart, Efficient adiabatic demagnetization refrigeration to below 50 mK with ultrahigh-vacuum-compatible ytterbium diphosphates AYbP_2O_7 ($A = \text{Na}, \text{K}$), *Phys. Rev. Appl.* **20**, 014013 (2023).
- [59] Research data supporting this work will be made available at: DOI:10.17863/CAM.123100.